

## RESEARCH ARTICLE

# An *in vitro* Study to Evaluate the Bioactivity of Osteoblast Cells on the Titanium Disk Coated with the Hydro Gel formulated from Acemannan and Curcuminoids

<sup>1</sup>Ramesh Chowdhary, <sup>2</sup>Praneeth R Pachimalla, <sup>3</sup>Sunil K Mishra

## ABSTRACT

**Background:** Recently, increasing attention has been paid to the potential of hydrophilic implant surfaces to further stimulate osseointegration.

**Purpose:** The main purpose of this study was to evaluate the cell viability with the Hydro gel formulated from acemannan and curcuminoids coated on titanium disks.

**Materials and methods:** Hydro gel formulated from acemannan and curcuminoids in different proportions were prepared and coated on the titanium disk and the bioactivity of Osteoblast cells (MG-63) was evaluated. The hydrogel was formulated in to 3 groups. Sample 1 (75% acemannan and 25% curcuminoid), sample 2 (50% acemannan and 50% curcuminoid) and sample 3 (25% acemannan and 75% curcuminoid). 3-(4,5-dimethylthiazol-2-yl)-2,5-diphenyltetrazolium bromide (MTT) assay was done to evaluate the cell viability. To exclude material's effect on the test and to see how the cells react during the assay, the MTT assay was also performed for the disks which were not seeded with the cell culture.

**Results:** Curcumin and acemannan had good cell viability from day 1, but then, the viability decreased. Acemannan showed less than 10% inhibition at 10 µg/mL when compared with curcumin and so acemannan in the formulation 10 µg/mL can be used. Osteoblastic differentiation (OD) of sample 1 at the end of 24 hrs was 0.0837 and over all % of cell inhibition was 75.65; for sample 2 at the end of 24 hrs OD was 0.2402 and overall % cell inhibition was 57.67%; for sample 3 at the end of 24 hrs OD was 0.1643 and over all % of cell inhibition was 75.62%.

**Conclusion:** Changes in concentration of hydrogel could not create any favourable condition for the proliferation of the cells, secondly the other condition was the use of cancerous cell line, turmeric previously showed to have tremendous effect on killing cancer cells which also might have contributed for the negative outcome of the result.

**Keywords:** Acemannan, Curcuminoids, Hydrophilic gel, MTT assay, Osseointegration, Titanium.

**How to cite this article:** Chowdhary R, Pachimalla PR, Mishra SK. An *in vitro* Study to Evaluate the Bioactivity of Osteoblast Cells on the Titanium Disk Coated with the Hydro Gel formulated from Acemannan and Curcuminoids. *Int J Prosthodont Restor Dent* 2018;8(1):22-27.

**Source of support:** Nil

**Conflict of interest:** None

## INTRODUCTION

Currently, dental implants have become an integral part of dentistry.<sup>1-3</sup> Enhancing of dental implant osseointegration has been an area of research for more than four decades now. Researchers have tried from macrogeometry to microgeometry, change in materials, drill sequences, etc., to enhance osseointegration.<sup>4-6</sup> It is well acknowledged that the overall success and survival of implants depend on the quality and quantity of host bone, presence of sufficient primary stability at the time of implant placement, and formation of a direct BIC. However, osseointegration and BIC are mainly enhanced by implant surface characteristics, such as surface topography, chemistry, roughness, and energy.<sup>7-10</sup>

Recently, increasing attention has been paid to the potential of hydrophilic implant surfaces to further stimulate osseointegration.<sup>9</sup> It was well documented that in an attempt to improve implant surface activity and osteopromotive activity, implants were coated with localized organic and inorganic osteogenic coatings on their surfaces.<sup>11</sup> It was suggested that hydro gels should be incorporated in the gel, as they are hydrophilic in nature and can give a sustained release of bone-proliferating medicine.<sup>2</sup>

Previously, herbal extracts were used in bone-healing process. Acemannan is extracted from aloe vera gel, and it is a biodegradable polysaccharide consisting of beta-acetylated polymannose. *In vitro* studies had shown that acemannan can stimulate gingival fibroblast, cementoblasts, dental pulp fibroblasts and lead to bone marrow-stromal cell proliferation and differentiation.<sup>12-14</sup> Since centuries, turmeric has been used as a dietary spice and as a traditional Indian medicine. Extracts obtained from the rhizome of turmeric (*Curcuma longa*), have been used as anti-inflammatory agents. In various experimental conditions and clinical settings, it was found that curcumin exhibits antibacterial, antioxidant, antifungal, antiviral, and anticancer activities.<sup>15-17</sup>

<sup>1,3</sup>Professor, <sup>2</sup>Postgraduate Student

<sup>1,2</sup>Department of Prosthodontics, RajaRajeswari Dental College & Hospital, Bengaluru, Karnataka, India

<sup>3</sup>Department of Prosthodontics, People's College of Dental Sciences & Research Centre, Bhopal, Madhya Pradesh, India

**Corresponding Author:** Ramesh Chowdhary, Professor Department of Prosthodontics, RajaRajeswari Dental College & Hospital, Bengaluru, Karnataka, India, e-mail: drammc@yahoo.com


The main aim of the present study was to formulate a hydrophilic gel to be used along with the dental implant placement to create a hydrophilic surface for the dental implant, to enhance implant-to-blood contact, but would also enhance the BIC. The study was a basic microbiological study and the aim of this study was to evaluate the influence of direct exposure of gel applied and nongel applied to titanium disks on the bioactivity of osteoblast cells (MG-63).

## MATERIALS AND METHODS

The study was approved by the institutional animal ethics committee of RajaRajeswari Dental College & Hospital, Bengaluru, India.

### Basic Microbiological Study

The study was done to find the long-term direct effect of hydrophilic gel on different cell lines. Viability of the cells and their differentiation were analyzed so that biocompatibility of the tested materials can be assessed. *In vivo* situation was simulated as closely as possible to evaluate the long-term effects of the gel on osteoblast cells. The hydrogel was formulated into three groups. Sample 1 (75% acemannan and 25% curcuminoid), sample 2 (50% acemannan and 50% curcuminoid), and sample 3 (25% acemannan and 75% curcuminoid) (Fig. 1). Disks of commercially pure titanium grade IV (ASTM F67) with diameter of 5 mm and thickness of 2 mm were used (Fig. 2). The oxide layers formed on the surface of the disks were removed by subjecting it to an acid treatment. Titanium disks were coated with the hydrophilic gel made from acemannan and curcuminoid in different combinations. For proper coating of gel around the disks and controlled release, the disks were immersed in gel for around 45 to 60 seconds.

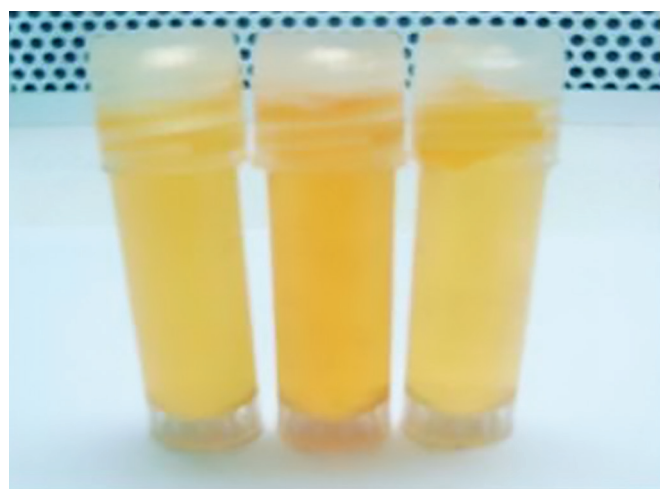

**Fig. 1:** Hydrophilic gel formulated from acemannan and curcuminoids in three different proportions

### Procedure

Trypsinized (70–80%) confluent cell lines (MG-63) were centrifuged and checked for the viability. The formulated hydrogel samples 1, 2, and 3 were put on each titanium disk. After half an hour, samples with titanium disks were placed in each 96-well plate. Seeded 50,000 cells/well in 96-well plate were incubated for 24 hours at 37°C in 5% CO<sub>2</sub> incubator. After 24 hours of incubation, the medium was removed and replaced with fresh medium and kept for next 24 hours for incubation and for cells to proliferate. After 24 hours, the medium was removed from the wells and 100 µL/well of the MTT (5 mg/10 mL of MTT in 1X PBS, the solution is filtered through a 0.2 µm filter and stored at 2 to 8°C for frequent use or frozen for extended periods) working solution was added and incubated for 3 to 4 hours. After incubation with MTT reagent, the medium was removed from the wells and 100 µL of dimethyl sulfoxide (DMSO) was added to rapidly solubilize the formazan. The absorbance was measured at 590 nm.

$$\% \text{ of inhibition} = 100 - \left( \frac{\text{sample}}{\text{control}} \right) \times 100$$

### Cell Viability

An MTT assay was conducted to determine cell viability; 12-well plates containing gel applied and non-gel applied disks were seeded with 10,000 cells per cm<sup>2</sup> and F12K (Kaighn's modification of Ham's F-12 medium) medium with 20% fetal calf serum (FCS) and 100 µg/gm streptomycin. During the experiment, the cell media were changed once a week. Nine wells per specimen in total at different time intervals were tested. The MTT solution was added to the cell medium after 24 hours, 7 days, 14 days, and 21 days. The cells were then incubated in the dark for 4 hours at 37°C. The cell medium



**Fig. 2:** Titanium disks 5 mm in diameter and 2 mm in width

was discarded subsequently and the cells were lysed with 0.004 N HCl in isopropanol. The cell lysates were centrifuged and supernatants were transferred as triplets to a 96-well plate. The adsorption was measured at 570 and 630 nm using a Synergy HT microplate reader (BioTek, Bad Friedrichshall, Germany).

In order to exclude the material's effect on the test and to see how the cells react during the assay, the MTT assay was also performed for the disks which were not seeded with the cell culture. Additionally, cell morphology was studied by inverted light microscopy using a microscope type 090-135.002 (Leica Microsystems GmbH, Wetzlar, Germany) equipped with a Nikon Ds-Fi1 digital camera (Nikon, Duesseldorf, Germany).<sup>18</sup>

### Alkaline Phosphatase Content

Senso Lyte pNPP alkaline phosphatase (ALP) assay (Ana Spec, Fremont, CA), which acts as an indicator of changes in the differentiation behavior of the bone-forming cells caused by the test substances, was applied after 24 hours, 7 days, 14 days, and 21 days of culturing in Dulbecco's modified Eagle's medium, low glucose with l-glutamine, 10% FCS, 100 U/mL penicillin, 100 µg/gm streptomycin, 0.1 µM dexamethasone, 0.005 µM ascorbic acid, and 10 mM β-glycerolphosphate to induce osteogenic differentiation. During the experiment, the cell media were changed in once a week. Nine wells per specimen in total at different time intervals were tested.

The cells were washed and frozen at -80°C. After thawing, the cell number was measured according to the manufacturer's protocol, using a PicoGreen dsDNA quantitation assay (Invitrogen, Eugene, OR); 1% Triton X-100 in phosphate-buffered saline was used to lyse the cells. The cell lysates were centrifuged in a 96-well plate,

and the supernatants were mixed with the PicoGreen<sup>®</sup> working solution. The excitations of the samples were done at 485 nm and the fluorescence emission intensity was measured at 528 nm. The cells lysed for the PicoGreen assay were centrifuged, and in specific assay, buffer dilution of the supernatants was done. The diluted samples were coated with ALP and the absorbance was measured at 405 nm. The absolute amounts of ALP were correlated with the cell numbers obtained from the PicoGreen assay. In order to exclude the material's effect on the test and to see how the cells react during the assay, both ALP and PicoGreen assays were also performed for the disks which were not seeded with the cell culture.<sup>18</sup>

### Statistical Analysis

Statistical Package for the Social Sciences (version 22, IBM, Corp.) software was used for statistical analysis. Mean and standard deviation were done to find the frequency distribution for continuous variables. Student's unpaired t-test was used to compare mean values between the two groups. The level of significance was set at  $p < 0.05$ .

## RESULTS

### Basic Microbiological Study

Curcumin and acemannan had good cell viability from day 1, but then the viability decreased (Tables 1 and 2). Osteoblastic differentiation (OD) of sample 1 at the end of 24 hours was 0.0837 and the overall cell inhibition was 75.65%; for sample 2, at the end of 24 hours, OD was 0.2402 and the overall cell inhibition was 57.67%; for sample 3, at the end of 24 hours, OD was 0.1643 and the overall cell inhibition was 75.62% (Table 3). Changes in concentration of hydrogel could not create any favorable

**Table 1:** Individual analysis of curcuminoids

Plant name	Concentration (µg/mL)	Absorbance 590 nm	% inhibition	IC <sub>50</sub>
Control	0.0	0.495	0.00	36.13 µg/mL
Curcumin	1.5	0.482	2.70	
	3.1	0.449	9.37	
	6.3	0.403	18.65	
	12.5	0.346	30.16	
	25.0	0.279	43.68	
	50.0	0.164	66.90	

**Table 2:** Individual analysis of acemannan

Plant name	Concentration (µg/mL)	Absorbance 590 nm	% inhibition	IC <sub>50</sub>
Control	0.0	0.347	0.00	Not applicable
Aloe vera	1.5	0.341	1.64	
	3.1	0.334	3.66	
	6.3	0.329	5.11	
	12.5	0.312	10.01	
	25.0	0.295	14.91	
	50.0	0.243	29.91	
	100.0	0.207	40.29	

**Table 3:** Absorbance values of effect of sample with titanium disk on MG-63 cells by MTT assay

Sample	OD (n = 1)	OD (n = 2)	OD (n = 3)	Average	% inhibition	Comment
(Control) only titanium disk	0.7288	0.6067	0.5061	0.6138	0.00	
Sample 1 + titanium disk	0.0837	0.195	0.1696	0.1494	75.65	No proliferation
Sample 2 + titanium disk	0.2402	0.3032	0.2361	0.2598	57.67	No proliferation
Sample 3 + titanium disk	0.1643	0.1334	0.1511	0.1496	75.62	No proliferation

condition for the proliferation of the cells, and secondly, the other condition was the use of cancerous cell line; turmeric previously showed to have tremendous effect on killing cancer cells which also might have contributed for the negative outcome of the result.

## DISCUSSION

Osseointegration results in structural and functional contact between implant surface and living bone.<sup>20</sup> Since the beginning of implant dentistry, attention has been paid to the design of implant surface topography for enhancing osseointegration.<sup>2,21,22</sup> Microsurface supports the transition from mechanical to biological stability, helping to minimize the risk of early complication.<sup>23</sup> Hydrophilic implant surface has also been used.<sup>24</sup> *In vitro* studies have shown that hydrophilic surface supports the adhesion of monocytes, platelet activation, and blood clot formation, which are the initial events in osseointegration.<sup>25,26</sup> Hydrophilic surfaces are favorable for the osteogenesis differentiation of mesenchymal stem cells and they demonstrated anti-inflammatory properties.<sup>27,28</sup>

This study looked at the direct long-term effect of hydrophilic gel on different cell lines. Cell viability, differentiation, and morphology as well as pH and calcium uptake were analyzed to assess the overall biocompatibility of the tested materials. We evaluated the long-term effects of the gel on osteoblast cells to simulate them in *in vivo* situation as closely as possible.

It was also shown in previous studies that acemannan polysaccharides extracted from aloe vera have negligible cytotoxicity and sound cytocompatibility.<sup>12</sup> Pure acemannan had high viability at the very first day, but then the viability decreased. Turmeric which has excellent anti-inflammatory and bone-healing properties<sup>15</sup> was added as a second ingredient to the gel.

An important drawback of tetrazolium-based tests is that the difference between cytotoxic (cell death) and cytostatic (reduced growth rate) effects cannot be distinguished.<sup>29</sup> We thus looked at cell morphology under light microscopy and transmission electron microscopy (TEM). After examination under TEM and light microscopy, it was revealed that the number of cells decreased in the presence of hydrophilic gel. Later, individual analysis of both the ingredients was done; in this, it was shown that curcumin had a very high percentage of cell inhibition, whereas acemannan had significantly better results, as it can be used until 10 µg/mL.

Degradation particles were also found in the cytoplasm. The presence of high amounts of degradation products inside the cells could explain the lower cell viability values for hydrophilic gel. It was shown in previous studies that the uptake of material particles leads to induction of cell stress which triggers cytotoxicity. Here in the present

study, we showed that the treatment of MG-63 cells with hydrophilic gel inhibited their proliferation. This result is consistent with previous studies performed in human<sup>30</sup> or rat<sup>31</sup> osteoblast and with others, indicating that curcumin inhibited the proliferation of several cell types, most likely due to an apoptosis-dependent mechanism.<sup>32</sup> This mechanism has not been completely elucidated, but it may be, at least in part, due to the ability of curcumin to suppress the activation of activator protein 1, a dimeric transcription factor consisting of a Fos-related osteoblast differentiation. During their developmental sequence, osteoblasts express genes associated with differentiation protein and a Jun-related protein. Osteoblast differentiation comprises three distinct processes: proliferation, maturation of the extracellular matrix, and mineralization.<sup>33-36</sup> We observed changes in the early stages, with increased ALP expression in curcumin-stimulated cells at 7 days postculture. However, there was a significant decrease in the late stages of osteoblast differentiation at day 21, evidenced by the decelerating accumulation of calcium in osteoblasts.

In previously reported studies, curcumin has been reported to cause the arrest of cell cycle and the upregulation of expression of p21WAF1/CIP1.<sup>37-39</sup> Furthermore, there is a report that p21WAF1/CIP1 mediates G1 arrest. Thus, the inhibitory effects of curcumin on proliferation of ROB cells might be due, in part, to the arrest of cell cycle progression via expression of p21WAF1/CIP1. In addition, curcumin inhibited the mineralization by ROB cells. Recently, p21WAF1/CIP1 has been reported to act as a brake in osteoblast differentiation by using p21WAF1/CIP1 null mice.<sup>40</sup> Furthermore, transient overexpression of p21WAF1/CIP1 from an adenovirus vector delayed the onset of differentiation both in wild-type and in p21WAF1/CIP1 null osteoblasts.<sup>39</sup>

Turmeric inhibition for cell proliferation could be supported by studies done by Notoya et al,<sup>31</sup> wherein they concluded that curcumin might be an inhibitor for metabolism of both cultured osteoblast and osteoclasts. Hence, this combination was prepared for the animal trials.

Future studies can be carried out which might include implant placement with hydrogel coating in patient with compromised wound healing (e.g., diabetes mellitus, osteoporosis, and postradiation therapy) and in clinical situation, such as immediate implant placement or implant placement with guided bone regeneration.

## CONCLUSION

Changes in concentration of hydrogel could not create any favourable condition for the proliferation of the cells, secondly the other condition was the use of cancerous cell line, turmeric previously showed to have tremendous effect on killing cancer cells which also might have contributed for the negative outcome of the result.

## ACKNOWLEDGMENT

This research was funded by Rajiv Gandhi University of Health Sciences, Bengaluru, Karnataka, India.

## REFERENCES

- Association of Dental Implantology. A dentist's guide to implantology. Surrey: ADI; 2012.
- Novaes AB Jr, de Souza SL, de Barros RR, Pereira KK, Iezzi G, Piattelli A. Influence of implant surfaces on osseointegration. *Braz Dent J* 2010 Mar;21(6):471-481.
- Vasak C, Busenlechner D, Schwarze UY, Leitner HF, Munoz Guzon F, Hefti T, Schlottig F, Gruber R. Early bone apposition to hydrophilic and hydrophobic titanium implant surfaces: a histologic and histomorphometric study in mini pigs. *Clin Oral Implants Res* 2014 Dec;25(12):1378-1385
- Schulz MC, Korn P, Stadlinger B, Range U, Möller S, Becher J, Schnabelrauch M, Mai R, Scharnweber D, Eckelt U, et al. Coating with artificial matrices from collagen and sulfated hyaluronan influences the osseointegration of dental implants. *J Mater Sci Mater Med* 2014 Jan;25(1):247-258.
- Chowdhary R, Jimbo R, Thomsen CS, Carlsson L, Wennerberg A. The osseointegration stimulatory effect of macrogeometry-modified implants: a study in the rabbit. *Clin Oral Implants Res* 2014 Sep;25(9):1051-1055.
- Chowdhary R, Halldin A, Jimbo R, Wennerberg A. Influence of micro threads alteration on osseointegration and primary stability of implants: an FEA and *in vivo* analysis in rabbits. *Clin Implants Dent Relat Res* 2015 Jun;17(3):562-569.
- Javed F, Romanos GE. The role of primary stability for successful immediate loading of dental implants. A literature review. *J Dent* 2010 Aug;38(8):612-620.
- Javed F, Almas K, Crespi R, Romanos GE. Implant surface morphology and primary stability: is there a connection? *Implant Dent* 2011 Feb;20(1):40-46.
- Gaviria L, Salcido JP, Guda T, Ong JL. Current trends in dental implants. *J Korean Assoc Oral Maxillofac Surg* 2014 Apr;40(2):50-60.
- Anil, S.; Anand, PS.; Alghamdi, H.; Jansen, JA. Dental implant surface enhancement and osseointegration. Rijeka: InTech Open Access Publisher; 2011. pp. 83-108.
- de Jonge LT, Leeuwenburgh SC, Wolke JG, Jansen JA. Organic-inorganic surface modifications for titanium implant surfaces. *Pharm Res* 2008 Oct;25(10):2357-2369.
- Boonyagul S, Banlunara W, Sangvanich P, Thunyakitpisal P. Effect of acemannan an extracted polysaccharide from Aloe vera on BMSCs proliferation, differentiation, extracellular matrix synthesis, mineralization, and bone formation in a tooth extraction model. *Odontology* 2014 Jul;102(2):310-317.
- Chantarawatit P, Sangvanich P, Banlunara W, Soontornvipart K, Thunyakitpisal P. Acemannan sponges stimulate alveolar bone, cementum and periodontal ligament regeneration in a canine class II furcation defect model. *J Periodontol Res* 2014 Apr;49(2):164-178.
- Jittapiromsak N, Sahawat D, Banlunara W, Sangvanich P, Thunyakitpisal P. Acemannan, an extracted product from Aloe vera, stimulates dental pulp cell proliferation, differentiation, mineralization, and dentin formation. *Tissue Eng Part A* 2010 Jun;16(6):1997-2006.
- Wright LE, Frye JB, Timmermann BN, Funk JL. Protection of trabecular bone in ovariectomized rats by turmeric (*Curcuma longa* L.) is dependent on extract composition. *J Agric Food Chem* 2010 Sep;58(17):9498-9504.
- Bharti AC, Takada Y, Aggarwal BB. Curcumin (diferuloylmethane) inhibits receptor activator of NF- $\kappa$ B ligand-induced NF- $\kappa$ B activation in osteoclast precursors and suppresses osteoclastogenesis. *J Immunol* 2004 May;172(10):5940-5947.
- von Metzler I, Krebbel H, Kuckelkorn U, Heider U, Jakob C, Kaiser M, Fleissner C, Terpos E, Sezer O. Curcumin diminishes human osteoclastogenesis by inhibition of the signalsome-associated I $\kappa$ B kinase. *J Cancer Res Clin Oncol* 2009 Feb;135(2):173-179.
- Charyeva O, Dakischew O, Sommer U, Heiss C, Schnettler R, Lips KS. Biocompatibility of magnesium implants in primary human reaming debris-derived cells stem cells *in vitro*. *J Orthopaed Traumatol* 2016 Mar;17(1):63-73.
- NDORMS. EQUATOR network identification of reporting guidelines (Search strategy for MEDLINE database). Oxford: NDORMS; 2017. [cited 2017 Dec 13]. Available from: [www.equator-network.org/resource-centre/](http://www.equator-network.org/resource-centre/).
- Albrektsson T, Albrektsson B. Osseointegration of bone implants: a review of an alternative mode of fixation. *Acta Orthop Scand* 1987 Oct;58(5):567-577.
- Buser D, Broggin N, Wieland M, Schenk RK, Denzer AJ, Cochran DL, Hoffmann B, Lussi A, Steinemann SG. Enhanced bone apposition to a chemically modified SLA titanium surface. *J Dent Res* 2004 Jul;83(7):529-533.
- Smeets R, Stadlinger B, Schwarz F, Beck-Broichsitter B, Jung O, Precht C, Kloss F, Grobe A, Heiland M, Ebker T. Impact of dental implant surface modifications on osseointegration. *Bio Med Res Int* 2016 Jun;2016:6285620.
- Zhao G, Schwartz Z, Wieland M, Rupp F, Geis Gerstorfer J, Cochran DL, Boyan BD. High surface energy enhances cell response to titanium substrate microstructure. *J Biomed Mater Res Part A* 2005 Jul;74(1):49-58.
- Schwarz F, Wieland M, Schwartz Z, Zhao G, Rupp F, Geis Gerstorfer J, Schedle A, Broggin N, Bornstein MM, Buser D, et al. Potential of chemically modified hydrophilic surface characteristics to support tissue integration of titanium dental implants. *J Biomed Mater Res B Appl Biomater* 2009 Feb;88(2):544-557.
- Milleret V, Tugulu S, Schlottig F, Hall H. Alkali treatment of microrough titanium surfaces affects macrophage/monocyte adhesion, platelet activation and architecture of blood clot formation. *Eur Cell Mater* 2011 May;21:430-444.
- Hong J, Kurt S, Thor A. A hydrophilic dental implant surface exhibit thrombogenic properties *in vitro*. *Clin Implants Dent Relat Res* 2013 Feb;15(1):105-112.
- Wall I, Donos N, Carlqvist K, Jones F, Brett P. Modified titanium surfaces promote accelerated osteogenic differentiation of mesenchymal stromal cells *in vitro*. *Bone* 2009 Jul;45(1):17-26.
- Hamlet S, Alfarsi M, George R, Ivanovski S. The effect of hydrophilic titanium surface modification on macrophage inflammatory cytokine gene expression. *Clin Oral Implants Res* 2012 May;23(5):584-590.
- Fischer J, Prosenc MH, Wolff M, Hort N, Willumeit R, Feyerabend F. Interference of magnesium corrosion with tetrazolium-based cytotoxicity assays. *Acta Biomater* 2010 May;6(5):1813-1823.
- Chan WH, Wu HY, Chang WH. Dosage effects of curcumin on cell death types in a human osteoblast cell line. *Food Chem Toxicol* 2006 Aug;44(8):1362-1371.

31. Notoya M, Tsukamoto Y, Nishimura H, Woo JT, Nagai K, Lee IS, Hagiwara H. Quercetin, a flavonoid, inhibits the proliferation, differentiation, and mineralization of osteoblasts *in vitro*. *Eur J Pharmacol* 2004 Feb;485(1-3):89-96.
32. Chen HW, Huang HC. Effect of curcumin on cell cycle progression and apoptosis in vascular, smooth muscle cells. *Br J Pharmacol* 1998 Jul;124(6):1029-1040.
33. Zheng X, Cheng M, Xiang L, Liang J, Xie L, Zhang R. The AP-1 transcription factor homolog *Pf*-AP-1 activates transcription of multiple biomineral proteins and potentially participates in *Pinctada fucata* biomineralization. *Sci Rep* 2015 Sep;5:14408.
34. McCabe LR, Kockx M, Lian J, Stein J, Stein G. Selective expression of fos- and jun-related genes during osteoblast proliferation and differentiation. *Exp Cell Res* 1995 May;218(1):255-262.
35. Huang W, Yang S, Shao J, Li Y. Signaling and transcriptional regulation in osteoblast commitment and differentiation. *Front Biosci* 2007 May;12:3068-3092.
36. Javed A, Chen H, Ghori FY. Genetic and transcriptional control of bone formation. *Oral Maxillofac Surg Clin North Am* 2010 Aug;22(3):283-293.
37. Park MJ, Kim EH, Park IC, Lee HC, Woo SH, Lee JY, Hong YJ, Rhee CH, Choi SH, Shim BS, et al. Curcumin inhibits cell cycle progression of immortalized human umbilical vein endothelial (ECV304) cells by up-regulating cyclin-dependent kinase inhibitor, p21WAF1/CIP1, p27KIP1 and p53. *Int J Oncol* 2002 Aug;21(2):379-383.
38. Zheng M, Ekmekcioglu S, Walch ET, Tang CH, Grimm EA. Inhibition of NF- $\kappa$ B and nitric oxide by curcumin induces G2/M cell cycle arrest and apoptosis in human melanoma cells. *Melanoma Res* 2004 Jun;14(3):165-171.
39. Bellosta, P, Masramon L, Mansukhani A, Basilico C. p21(WAF1/CIP1) acts as a brake in osteoblast differentiation. *J Bone Miner Res* 2003 May;18(5):818-826.
40. Deng C, Zhang P, Haepel JW, Elledge SJ, Leder P. Mice lacking p21CIP1/WAF1 undergo normal development, but are defective in G1 checkpoint control. *Cell* 1995 Aug;82(4):675-684.